

A Revised Method for the Determination of Major and Trace Elements in Iron Meteorites by Neutron Activation Analysis

By

Masako SHIMA

Department of Physical Sciences, National Science Museum, Tokyo.

Sadayo YABUKI, Takashi KIMURA and Hideo YABUKI

The Institute of Physical and Chemical Research, Wako, Saitama.

I. Introduction

The distribution of trace elements in iron meteorites is an important factor for the discussion of the evolution of iron meteorites through condensation, accretion and/or fractionation processes of the elements. For such a purpose it is necessary to obtain data of similar quality for each element belonging to the same group, such as Cr-Mo-W, Cu-Ag-Au or so. Recently a number of superior analyses of trace elements in iron meteorites have been reported (COBB, 1967; CROCKET, 1972; KRACHER *et al.*, 1980; REED, 1972; SCHAUDY *et al.*, 1972; SCOTT *et al.*, 1973, 1976; SEARS, 1978; SEITNER *et al.*, 1971; SMALES *et al.*, 1967; WASSON *et al.*, 1971; WILLIS, 1981). Most of these studies are, however, limited to the determination of single elements or of several indicator elements for the classification of iron meteorites.

We have been engaged in the determination by neutron activation analysis of trace elements in Japanese iron meteorites in order to obtain useful data for cosmochemical discussions as well as to help in their classification. Since the analytical method was reported by one of the authors two years ago (SHIMA, 1979), the procedures have been revised in such a way as to give better results.

In this paper, we present the improved method of neutron activation analysis of iron meteorites.

II. Experimental Procedure

To cover all major and trace elements to be analyzed, three different methods of neutron activation analysis, instead of four as in the previous paper (SHIMA, 1979), were planned. Some elements are determined by only one of these methods and some others can be analyzed by all three. The analytical results obtained from different methods can be used not only for the comparison of each method but also for checking the homogeneity of the elements in the meteorites.

A. Monitors

Thermal neutron monitors were prepared in the same way as described in the previous paper. An attempt was also made to calculate γ -ray activities using only one or two representative elements. This aim only succeeded in the case of experimental conditions with rather long irradiation periods and with nuclides showing comparatively simple γ -decay.

B. Methods and Procedure

In these experiments neutron irradiation were performed in the following four reactors: JRR-2, JRR-3 and JRR-4 of Japan Atomic Energy Research Institute, Tokai, and TRIGA Mark II of St. Paul's University, Yokosuka.

1. Non-destructive thermal neutron activation analysis

Besides major elements, *i.e.* Co and Ni, some trace elements can be determined by this procedure. The radiochemical data on (n, γ) reactions by thermal neutrons used for this procedure are presented in Table 1. Because of the low contents of some elements in some meteorites analyzed, some of the nuclides in this table could not be detected in the practical measurements.

In the mean time, it was noticed that higher specific activities could be obtained for the required elements by irradiation with a higher neutron flux for a shorter time, because ^{59}Fe and ^{60}Co produced from main component of iron meteorites have relatively long half lives.

The neutron irradiation condition was changed from a thermal neutron flux of 1.5×10^{12} neutrons/cm²·sec for 1 and 6 hours (TRIGA Mark II) to 8×10^{13} neutrons/cm²·sec for 40 minutes (JRR-4). About 50 mg of each meteorite specimen was used in this procedure. After 1 to 2 hours cooling, the irradiated meteorite samples and monitors are analyzed with a Ge (Li) γ -ray spectrometer.

2. Radiochemical neutron activation analysis—1

Because one of major purposes of this method is the determination of trace amounts of germanium using ^{75}Ge (half life 82.78 min.), it is necessary to count its γ -ray activity within 1 or 2 hours after thermal neutron irradiation of iron meteorites. The Al-capsule commonly utilized for neutron irradiation is not adequate for this purpose because of high specific activities produced from impurity elements in Al. Therefore, polyimid capsules were used in this experiment.

The radiochemical data for the elements analyzed by this procedure are listed in Table 2.

About 50 mg of sample was weighed accurately, sealed in a quartz tube and irradiated at a flux of 8×10^{13} or 5.5×10^{13} neutron/cm²·sec for 6 or 12 hours in JRR-4 or at a flux of 2×10^{13} neutron/cm²·sec for 24 or 30 hours in JRR-3. Monitors were also sealed in quartz tubes and irradiated simultaneously with samples. Soon after irradiation, chemical separation of meteorite samples and Ge monitors were performed as quickly as possible.

Fig. 1 shows the schematic diagram of the post-irradiation chemistry which has

Table 1. Nuclear data on (n, γ) reaction used for instrumental Neutron activation analysis in this work.

Stable nuclides	Isotopic abundances* (%)	Therm. neut. cross section** (burns)	Radio-nuclides produced	Half life**	Energies used for determination** (kev)	Relative intensity**
⁵⁸ Fe	0.3	1.14	⁵⁸ Fe	44.56 d	{ 1099.2 1291.6	(56.5 %) (43.5 %)
⁶⁴ Ni	0.91	1.49	⁶⁵ Ni	2.520 h	{ 366.3 1115.5 1481.8	20.3 64.4 100 (23.5 %)
⁵⁸ Co	100	37	⁶⁰ Co	5.2719y	{ 1173.2 1332.5	100 100 (100 %)
⁵⁰ Cr	4.35	15.9	⁵¹ Cr	27.701 d	320.0	(10.2 %)
⁶³ Cu	69.17	4.4	⁶⁴ Cu	12.700 h	1345.6	(0.6 %)
⁷¹ Ga	39.9	4.6	⁷² Ga	14.12 h	{ 629.9 834.0 894.2 2201.6 2491.0 2507.7	25.5 100 (95.6 %) 10.3 27.3 7.8 13.4
⁷⁴ Ge	36.5	0.53	⁷⁵ Ge	82.78 m	264.6	(11.1 %)
⁷⁶ Ge	7.8	0.16	⁷⁷ Ge	11.30 h	264.6	(53.3 %)
⁷⁵ As	100	4.4	⁷⁶ As	26.33 h	{ 559.1 657.0 1216.0	100 13.5 7.57 (45.2 %)
¹⁰⁹ Pd	26.46	11	¹⁰⁹ Pd	13.427 h	88.05	(3.6 %)
¹¹⁵ In	95.7	71	^{116m} In	54.13 m	{ 138.3 818.7 1752.4	(3.33%) (11.6 %) (2.44%)
¹⁸⁸ Re	37.40	111	¹⁸⁸ Re	90.65 h	137.2	(9.4 %)
¹⁸⁷ Re	62.60	75	¹⁸⁸ Re	16.98 h	155.0	(15.3 %)
¹⁰¹ Ir	37.3	941	¹⁰² Ir	74.18 d	{ 295.9 316.5 468.1	34.64 100 (82.9 %) 58.1
¹⁰³ Ir	62.7	110	¹⁰⁴ Ir	19.15 h	{ 328.4 645.1 938.7	100.0 (13.0 %) 8.94 4.57
¹⁹⁸ Pt	7.2	3.7	¹⁹⁹ Pt	30.8 m		
				↓ β^-		
			¹⁹⁹ Au	3.148 d	158.2	(39 %)
¹⁹⁷ Au	100	98.8	¹⁹⁸ Au	2.697 d	411.8	(95.5 %)

* Data obtained from "Atomic Weight of the Elements 1979." by HOLDEN (1980).

** Data obtained from "Table of Isotopes." WILEY (1978). Values in parentheses in the 7th column are absolute γ -ray intensities of respective nuclides.

been modified in several points from the previous work. Before starting the sample decomposition, carrier mixture solutions were treated with conc. NH₄OH and dried with moderate heat in a distillation flask. The procedure consists of the distillation of groups of Ge and Re, and Ru and Os and precipitation of Mo, W, Ir, Pd, Pt, Au, Cd, As and Sb by H₂S in dilute acidic media followed by anion exchange separation.

Table 2. Nuclear data on (n, γ) reaction used for radiochemical neutron activation analyses—1.

Stable nuclides	Isotopic abundances* (%)	Therm. neut. cross section** (burns)	Radio-nuclides produced	Half life**	Energies used for determination** (kev)	Relative intensity
^{74}Ge	36.5	0.53	^{76}Ge	82.78 m	{ 198.56 264.6	103 1000 (11.1 %)
^{76}Ge	7.8	0.16	^{77}Ge	11.30 h	{ 210.9 215.7 264.6	58 53 100 (53 %)
^{75}As	100	4.4	^{76}As	26.33 h	{ 559.1 657.0 (1216.0)	100 (45.2 %) 13.5 7.57
^{98}Mo	24.13	0.13	^{98}Mo	66.02 h	{ 140.5 181.1 739.4	704 49.9 100 (12.7 %)
^{96}Ru	5.52	0.26	^{97}Ru	2.88 d	{ 215.7 (324.6)	100.5 (86.1 %) 11.9 ₅
^{102}Ru	31.6	1.3	^{103}Ru	39.36 d	{ 497.1 (610.3)	100 (86.4 %) 6.3
^{104}Ru	18.7	0.48	^{105}Ru	4.44 h	{ 469.4 676.4 724.2	37.1 33.1 100 (48 %)
^{108}Pd	26.46	11	^{109}Pd	13.427 h	88.05	(3.6 %) (50.1 %)
^{114}Cd	28.72	0.30	^{115}Cd	53.38 h	{ 336.2 492.1 527.7	148 31.2 100.5
^{121}Sb	57.3	6.2	^{122}Sb	2.681 h	{ 564.1 692.8	100 (70.4 %) 5.57
^{186}W	28.6	38	^{187}W	23.86 h	{ 134.2 479.5 685.8	40.5 100 (\approx 21 %) 125
^{185}Re	37.40	111	^{186}Re	90.65 h	137.2	(9.4 %)
^{187}Re	62.60	75	^{188}Re	16.98 h	{ 155.0 (478.0) (633.0)	930 (15.3 %) 64.9 77.7
^{192}Os	41.0	2.0	^{193}Os	30.6 h	{ 73.0 138.9 460.5	82 109 100.5 (3.95 %)
^{191}Ir	37.3	941	^{192}Ir	74.18 d	{ (295.9) 316.5 468.1	34.64 100 (82.9 %) 58.1
^{193}Ir	62.7	110	^{194}Ir	19.15 h	{ 328.4 (645.1) (938.7)	100.0 (13.0 %) 8.94 4.57
^{196}Pt	25.3	0.76	^{197}Pt	18.3 h	{ 77.4 (191.4)	100 (17 %) 20.5
^{195}Pt	7.2	3.7	^{196}Pt	30.8 m		
				$\downarrow \beta^-$		
			^{196}Au	3.148 d	{ 158.2 (208.2)	100 (39 %) 22.1
^{197}Au	100	98.8	^{198}Au	2.697 d	411.8	(95.5 %)

* Data obtained from "Atomic Weight of the Elements 1979." by HOLDEN (1980).

** Data obtained from "Table of Isotopes." WILEY (1978). Values in parentheses in the 6th column are energies used not for all samples, and in the 7th column are absolute γ -ray intensities of respective nuclides.

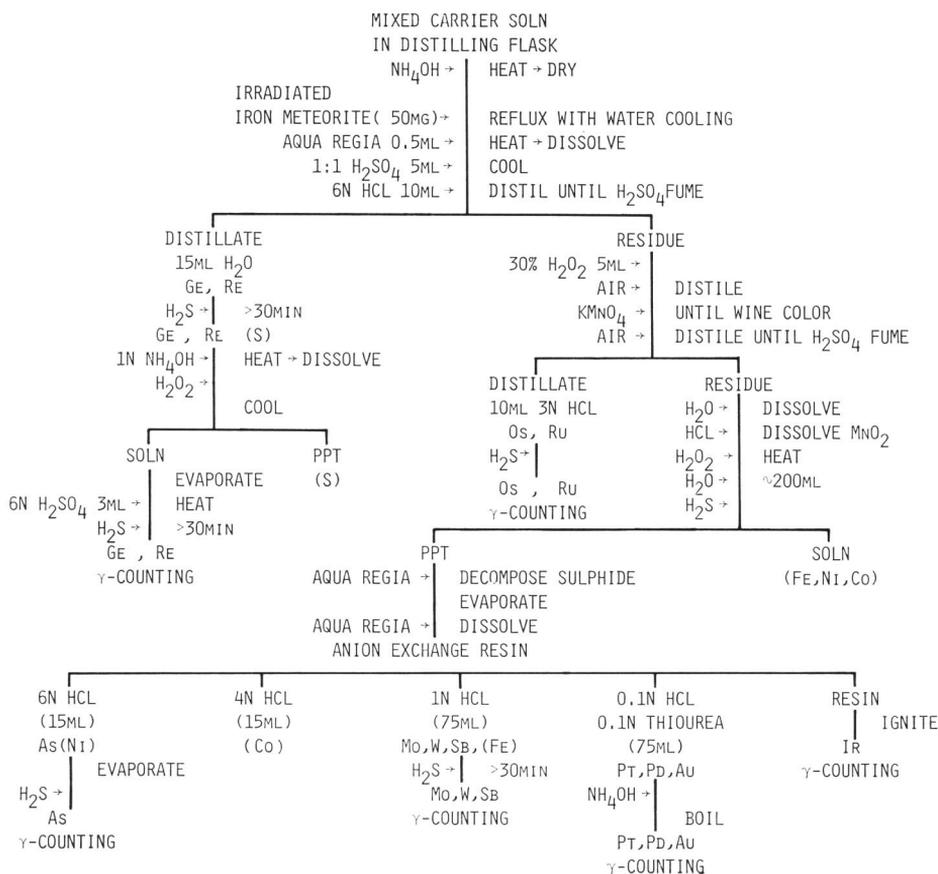


Fig. 1. Schematic diagram of the post-irradiation chemistry used for the radiochemical neutron activation analysis—1.

The distillation apparatus used in this work are shown in Fig. 2. Separated fraction of Ge-Re, As, Ru-Os, Mo-W-Sb and Pt-Pd-Au are precipitated as sulfides and analyzed with a Ge (Li) γ -ray spectrometer. The Ir fraction was obtained by igniting the anion exchange resin to ash after eluting all of other elements.

3. Radiochemical neutron activation analysis—2

Nuclides with half lives longer than 2 days were analyzed as follows and the radiochemical data are tabulated in Table 3.

Accurately weighed samples and monitors sealed in quartz tubes were irradiated in JRR-2 reactor at a flux of 3×10^{13} neutrons/cm²·sec for about 266 hours.

The post irradiation chemistry is schematically illustrated in Fig. 3. The same distillation apparatus as the former method was also used here. Though the new method is still composed of several steps of distillation, precipitation, Na₂CO₃ fusion

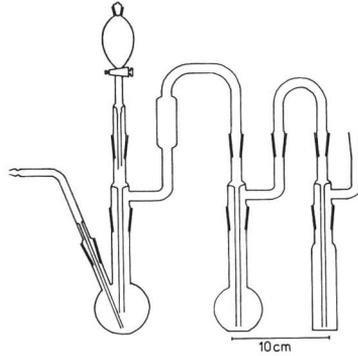


Fig. 2. Distillation apparatus for Ge, Ru, Os and Re.

Table 3. Nuclear data on (n, γ) reaction used for radiochemical neutron activation analyses—2

Stable nuclides	Isotopic abundances* (%)	Therm. neut. cross section** (burns)	Radio-nuclides produced	Half life**	Energies used for determination*** (kev)	Relative intensities**
^{50}Cr	4.35	15.9	^{51}Cr	27.701 d	320.0	(10.2 %)
^{64}Zn	48.6	0.78	^{65}Zn	244.0 d	1115.5	(50.75 %)
^{75}As	100	4.4	^{76}As	26.33 h	{ 559.1 657.0 (1216.0)	100 (45.2 %) 13.5 7.57
^{98}Mo	24.13	0.13	^{99}Mo	66.02 h	{ 140.5 181.1 739.4	704 49.9
^{96}Ru	5.52	0.26	^{97}Ru	2.88 d	{ 215.8 (324.6)	100 (12.7 %) 11.9 ₅
^{102}Ru	31.6	1.3	^{103}Ru	39.36 d	{ 497.0 610.3	100 (86.1 %) 6.3
^{100}Ag	48.17	4	$^{110\text{m}}\text{Ag}$	252.2 d	{ 657.7 884.7 937.5	1000 (94.4 %) 771 363
^{121}Sb	57.3	6.2	^{122}Sb	2.681 d	564.1	(70.4 %)
^{123}Sb	42.7	4.0	^{124}Sb	60.20 d	{ 602.7 722.8 1691.0	(98.3 %) (11.3 %) (49.1 %)
^{185}Re	37.40	111	^{186}Re	90.65 h	{ (122.6) 137.2	15.7 (9.4 %) 246
^{184}Os	0.020	3.0×10^3	^{185}Os	93.7 d	{ 646.1 874.8 880.3	10000 (81 %) 849 677
^{190}Os	26.4	13	^{191}Os	15.4 d	129.4	(26 %)
^{191}Ir	37.3	941	^{192}Ir	74.18 d	{ 295.8 316.5 468.1	34.64 (82.9 %) 100 58.1
^{197}Au	100	98.8	^{198}Au	2.697 d	411.8	(95.5 %)

* Data obtained from "Atomic Weight of the Elements 1979," by HOLDEN (1980).

** Data obtained from "Table of Isotopes," WILEY (1978). Values in parentheses in the 6th column are energies used not for all samples, and in the 7th column are absolute γ -ray intensities of respective nuclides.

Table 4. Nuclear data on (n, γ) reaction used for measurements of chemical yields.

Stable nuclides	Isotopic abundances* (%)	Therm. neut. cross section** (burns)	Radio-nuclides produced	Half life**	Energies used for determination*** (kev)	Relative intensities
⁵⁰ Cr	4.35	15.9	⁵¹ Cr	27.701 d	320.0	(10.2 %)
⁶⁸ Zn	18.8	0.072	^{68m} Zn	13.76 h	438.7	(94.8 %)
⁷⁴ Ge	36.5	0.53	⁷⁵ Ge	82.78 m	{198.56 264.6	103 1000 (11.1 %)
⁷⁶ Ge	7.8	0.16	⁷⁷ Ge	11.30 h	{210.9 215.7 264.6	58 53 100 (53 %)
⁷⁵ As	100	4.4	⁷⁶ As	26.33 h	{559.1 657.0 1216.0	100 13.5 7.57 (45.2 %)
⁹⁵ Mo	24.13	0.13	⁹⁹ Mo	66.02 h	{(140.5) 181.1 739.4	704 49.9 100 (12.7 %)
⁹⁶ Ru	5.52	0.26	⁹⁷ Ru	2.88 d	215.7	100 (86.1 %)
¹⁰⁴ Ru	18.7	0.48	¹⁰⁵ Ru	4.44 h	{(316.4) 469.4 676.4 724.2	23.6 37.1 33.1 100 (48 %)
¹⁰⁵ Pd	26.46	11	¹⁰⁹ Pd	13.427 h	{88.05 (311.41)	1.48 × 10 ⁴ (3.6 %)
¹¹⁰ Pd	11.72	0.02	^{111m} Pd	5.5 h	{169.5 391.3	14.3 100 (5.3 %)
¹⁰⁹ Ag	48.17	4	^{110m} Ag	252.2 d	{657.7 884.7 937.5	1000 771 363 (94.4 %)
¹¹⁰ Cd	12.51	0.10	^{111m} Cd	48.6 m	{(149.6) 246	34.6 100 (94.2 %)
¹¹⁴ Cd	28.72	0.30	¹¹⁵ Cd	58.38 h	{336.2 492.1 527.7	148 31.2 100.5 (50.1 %)
¹¹⁶ Cd	7.47	{0.051 0.025	¹¹⁷ Cd	2.43 h	{273.3 1576.8	100 38.6 (29 %)
			^{117m} Cd	3.32 h	{(1066.0) 1997.5	100 110 (23 %)
¹²¹ Sb	57.3	6.2	¹²² Sb	2.681 d	{564.1 (692.8) (1140)	100 5.57 1.17 (70 %)
¹⁸⁶ W	28.6	38	¹⁸⁷ W	23.86 h	{134.2 479.5 685.8	40.5 100 (≈21 %) 125
¹⁸⁷ Re	62.60	75	¹⁸⁸ Re	16.98 h	{155.0 (478.0) (633.0)	930 64.9 77.7 (15.3 %)
¹⁹² Os	41.0	2.0	¹⁹⁸ Os	30.6 h	{73.0 138.9 (280.4) 460.5 (557.4)	82 109 31.5 100 (3.95%) 33
¹⁹³ Ir	62.7	110	¹⁹⁴ Ir	19.15 h	{(293.5) 328.4 645.1 (938.7)	19.6 100.0 (13.0 %) 8.94 4.57

^{196}Pt	25.3	0.76	^{197}Pt	18.3 h	{ (77.4)	100	(17 %)
^{198}Pt	7.2	3.7	^{199}Pt	30.8 m	{ 191.4	20.5	
				$\downarrow \beta^-$			
			^{199}Au	3.148 d	{ 158.2	100	(39 %)
			^{198}Au	2.697 d	{ (208.2)	22.1	
^{197}Au	100	98.8			411.8		(95.5 %)

* Data obtained from "Atomic Weight of the Elements 1979." by HOLDEN (1980).

** Data obtained from "Table of Isotopes." WILEY (1978). Values in parentheses in the 6th column are energies used not for all samples, and in the 7th column are absolute γ -ray intensities of respective nuclides.

Table 5. Results of INAA.

Element	Okano	Tendo	Kuga	Tanakami	Shirahagi	Shirahagi No. 2. (Saotome)	Zaisho
Ni (%)	4.62 ± 0.06	8.70 ± 0.25	9.12 ± 0.45	—	7.86 ± 0.19	7.86 ± 0.29	7.2 ± 0.4
Co "	0.44 ± 0.01	0.435 ± 0.007	0.59 ± 0.05	0.49 ± 0.01	0.455 ± 0.011	0.4 ± 0.1	0.53 ± 0.01
Cr (ppm)	—	29 ± 3	14.9 ± 1.2	70 ± 6	278 ± 12	231 ± 5	6.55 ± 0.14
Cu "	614 ± 25	149 ± 7	116 ± 9	76 ± 5	194 ± 4	165 ± 12	182 ± 6
Ga "	56 ± 1	24.8 ± 2.1	16.7 ± 0.5	15.6 ± 0.4	2.6 ± 0.2	2.5 ± 0.1	13.1 ± 0.3
Ge "	174 ± 11	{ 54 ± 23 22.9 ± 0.6	29.5 ± 0.5	25.5 ± 0.6	—	—	—
As "	5.6 ± 1.3	7.0 ± 0.3	30.6 ± 0.2	7.4 ± 0.2	4.4 ± 0.2	3 ± 1	24.7 ± 0.5
Re "	0.72 ± 0.01	0.033 ± 0.004	—	< 0.08	0.27 ± 0.02	0.57 ± 0.03	< 0.06
Ir "	11.6 ± 0.2	0.27 ± 0.07	0.028 ± 0.004	0.11 ± 0.01	2.89 ± 0.08	2.7 ± 0.7	0.034 ± 0.005
Pd "	1.8 ± 0.2	3.44 ± 0.10	3.9 ± 0.4	2.2 ± 0.2	3.3 ± 0.4	3.1 ± 0.1	3.9 ± 0.1
Pt "	—	7.0 ± 0.8	7.7 ± 0.3	6 ± 1	—	—	—
Au "	0.47 ± 0.01	1.86 ± 0.02	2.2 ± 0.3	0.85 ± 0.02	0.90 ± 0.02	1.1 ± 0.3	2.09 ± 0.07
In "	—	0.019 ± 0.004	—	—	< 0.025	0.022 ± 0.002	—

were determined with a Ge (Li) γ -ray spectrometer.

III. Results and Discussion

The results obtained by the procedures 1 to 3 are summarized in Table 5, 6 and 7, respectively. Although the results from procedure 3 are still preliminary ones, data obtained by the three methods agree rather well. Some elements in certain iron meteorites give distinct values, possibly due to inhomogeneity of the sample.

It has been said that two iron meteorites were found on the bed of Shirahagi river in Toyama Prefecture, Japan, in 1890 and 1892. They were named after the localities, Shirahagi and Saotome. Saotome was long hidden and was recently found again. Metallographical observation shows that both of them belong to the fine octahedrite

Table 6. Results of RNNA-1 (ppm).

Element	Tendo	Kuga	Tanakami	Shirahagi	Shirahagi No. 2 (Saotome)	Zaisho
Ge	{ 24.8±0.9 53±2	28.6±0.4	48±2	0.12	0.127±0.007	85±3
As	9.0±0.6	24.0±2.4	7.0±0.1	4.3±0.6	4.7±0.1	32.9±0.9
Sb	0.2±0.1	0.23±0.02	0.046±0.005	0.022±0.002	0.018±0.004	0.37±0.02
Mo	7.0±0.3	7.6±0.5	8.5±0.6	5.7±0.4	6.3±1.4	5.8±0.2
W	0.53±0.06	0.21±0.1	2.9±0.2	4.9±1.1	3.8±0.3	1.2±0.3
Re	—	—	0.012±0.004	0.39±0.10	0.26±0.01	0.0016 ±0.0006
Ru	1.8±0.4	{ 1.2±0.6 0.43±0.05	2.73±0.13	2.0±0.2	1.7±0.4	0.37±0.04
Os	0.35±0.03	0.4±0.1	0.26±0.02	8±2	6.0±0.3	0.20±0.03
Ir	0.37±0.10	0.07±0.01	0.56±0.02	3.2±0.1	3.72±0.02	0.18±0.03
Pd	3.3±0.3	3.8±0.2	3.50±0.05	3.3±0.3	3.2±0.6	6.0±0.2
Pt	9.6±0.4	7.9±0.1	6.8±0.2	8.5±2.4	6.6±0.1	1.4±0.1
Au	1.18±0.07	2.3±0.2	1.00±0.02	0.97±0.03	0.96±0.03	1.5±0.1
Cd	—	—	0.009±0.003	—	—	0.044±0.002

Table 7. Preliminary results of RNAA-2 (ppm).

Element	Tendo	Kuga	Shirahagi
Cr	3±1	1.3±0.1	103±10
As	8.5±0.8	3.65±0.09	3.9±0.1
Sb	0.130±0.002	0.37±0.11	0.018±0.002
Mo	8.9±0.5	8.3±0.5	6.0±0.8
Re	0.2±0.1	—	0.36±0.04
Ru	5.9±0.2	{ 1.24±0.19 0.4±0.1	—
Os	0.12±0.02	0.2±0.1	—
Ir	—	0.04±0.01	2.4±0.6
Ag	0.012±0.001	0.005±0.001	0.011±0.002
Au	1.19±0.03	2.4±0.1	0.97±0.06

class. Judging from the resemblance of their chemical compositions determined in this work together with metallographic observation between Shirahagi and the newly found meteorite, the so-called Saotome, we conclude that these meteorite must have been originated from the same mass in space. From this point of view, Saotome should be renamed Shirahagi No. 2.

Ga, Ge and Ir have been usually used as the indicator elements for the classification of iron meteorites. The present results confirm the classification made by one of us (SHIMA *et al.*, 1978; SHIMA, 1979), *i.e.* Tendo, Kuga, Tanakami and Shirahagi as IIIA, IIIB, IIIE and IVA, respectively. Other two meteorites Okano and Shirahagi No. 2 (Saotome) are classified by the present data as IIA and IVA, respectively.

Cosmochemical discussions and reports of analyses of other iron meteorites will

be made elsewhere.

IV. Acknowledgement

The author express their sincere gratitude to Professor Y. ITO, Mr. T. TAKANO and other personnel in Tokai Branch, Research Center for Nuclear Sciences and Technology, the University of Tokyo. Thanks are also due to Professors K. TOMURA and F. SHIRAISHI and other individuals of St. Paul's University for their assistance in this work. Samples were irradiated in the reactors JRR-2, JRR-3 and JRR-4 of Japan Atomic Energy Research Institute, Tokai and TRIGA Mark II of St. Paul's University. This work was supported by National Universities' Program for the Common Use of JAERI Facilities and that of Atomic Energy Institute, St. Paul's University Facilities, the Ministry of Education, Science and Culture.

References

- COBB, J. C., 1967. A trace-element study of iron meteorites. *J. Geophys. Res.*, **72**: 1329–1341.
- CROCKET, J. H., 1972. Some aspects of the geochemistry of Ru, Os, Ir and Pt in iron meteorites. *Geochim. Cosmochim. Acta*, **36**: 517–535.
- HOLDEN, N. E., 1980. Atomic Weight of the elements 1979. *Pure Appl. Chem.*, **52**: 2349–2384.
- KRACHER, A., J. WILLIS and J. T. WASSON, 1980. Chemical classification of iron meteorites IX. A new group (IIF), revision of IAB and IIICD and data on 57 additional irons. *Geochim. Cosmochim. Acta*, **44**: 773–787.
- LEDERER, C. M. and V. S. SHIRLEY (editors), 1978. Table of isotopes. John Wiley & Sons, New York.
- REED, S. J. B., 1972. Determination of Ni, Ga, and Ge in iron meteorites by X-ray fluorescence analysis. *Meteoritics*, **7**: 257–262.
- SCHAUDY, R., J. T. WASSON and R. F. BUCHWALD, 1972. The chemical classification of iron meteorite VI. A reinvestigation of irons with Ge concentrations lower than 1 ppm. *Icarus*, **17**: 174–192.
- SCOTT, E. R. D., J. T. WASSON and V. E. BUCHWALD, 1973. Chemical classification of iron meteorite VII. A reinvestigation of iron with Ge concentration 25 and 80 ppm. *Geochim. Cosmochim. Acta*, **37**: 1957–1983.
- SCOTT, E. R. D. and J. T. WASSON, 1976. Chemical classification of iron meteorites. VIII. Group IC, IIE, IIF and 97 other irons. *Geochim. Cosmochim. Acta*, **40**: 103–115.
- SHIMA, MASAKO, A. OKADA, Y. OMORI, T. MASUDA and Y. TANAKA, 1978. Japanese iron meteorites: Chemical composition and microanalytical observation of Kuga, Shirahagi, Tanakami and Tendo. *Bull. Natn. Sci. Mus., Ser. E*, **1**: 1–18.
- SHIMA, MASAKO, 1979. The determination of major and trace elements in iron meteorites by neutron activation analysis. *Bull. Natn. Sci. Mus., Ser. E*, **2**: 1–16.
- SEARS, D. W., 1978. Condensation and the composition of iron meteorites. *Earth Planet. Sci. Letts*, **41**: 128–138.
- SEITNER, H., W. KIESL, F. KLUGER and F. HECHT, 1971. Wet-chemical analysis and determination of trace elements by neutron activation in meteorites. *J. Radioanal. Chem.*, **7**: 235–248.
- SMALES, A. A., D. MAPPER and K. F. FOUCHE, 1967. The distribution of some trace elements in meteorites as determined by neutron activation. *Geochim. Cosmochim. Acta*, **31**: 673–720.

- WASSON, J. T. and R. SCHAUDY, 1971. The chemical classification of iron meteorites. V. Group IIC and IID and other irons with germanium concentrations between 1 and 25 ppm. *Icarus*, **14**: 59–70.
- WILLIS, J. 1981. Antimony in iron meteorites. *Earth Planet. Sci. Letts*, **53**: 1–10.